

NRC Publications Archive Archives des publications du CNRC

Performance Improvement of Green Composites Using Nanoclays

Singh, Rajinder Pal; Ngo, Tri-Dung; Hu, Wei; Ton-That, Tan Minh; Denault, Johanne

NRC Publications Archive Record / Notice des Archives des publications du CNRC :

<https://nrc-publications.canada.ca/eng/view/object/?id=a576abc8-e98e-4128-86da-05662b3b047e>

<https://publications-cnrc.canada.ca/fra/voir/objet/?id=a576abc8-e98e-4128-86da-05662b3b047e>

Access and use of this website and the material on it are subject to the Terms and Conditions set forth at

<https://nrc-publications.canada.ca/eng/copyright>

READ THESE TERMS AND CONDITIONS CAREFULLY BEFORE USING THIS WEBSITE.

L'accès à ce site Web et l'utilisation de son contenu sont assujettis aux conditions présentées dans le site

<https://publications-cnrc.canada.ca/fra/droits>

LISEZ CES CONDITIONS ATTENTIVEMENT AVANT D'UTILISER CE SITE WEB.

Questions? Contact the NRC Publications Archive team at

PublicationsArchive-ArchivesPublications@nrc-cnrc.gc.ca. If you wish to email the authors directly, please see the first page of the publication for their contact information.

Vous avez des questions? Nous pouvons vous aider. Pour communiquer directement avec un auteur, consultez la première page de la revue dans laquelle son article a été publié afin de trouver ses coordonnées. Si vous n'arrivez pas à les repérer, communiquez avec nous à PublicationsArchive-ArchivesPublications@nrc-cnrc.gc.ca.

Title:

Performance Improvement of Green Composites Using Nanoclays

Rajinder Pal SINGH, Tri-Dung NGO, Wei HU, Tan Minh TON-THAT, and Johanne DENAULT*
Industrial Materials Institute, National Research Council of Canada
75 De Mortagne Blvd., Boucherville, Quebec, Canada J4B 6Y4

ABSTRACT

The role of nanoclays on the performance improvement of structural composites made from epoxy and flax fibers was investigated. The nanoclays were at first dispersed in the epoxy resin before the impregnation the flax fiber fabric. The results obtained demonstrate that specific treatment of the fiber surface can bring up the performance of composites such as the tensile strength, tensile modulus and the interfacial strength of the composites. However, the level of improvement on the properties of the composites is much better in the presence of dispersed nanoclays. In principle, the composite strength and modulus are mainly controlled by the fibers if the fiber-matrix interface is optimized. Thus the observed improvements in composite strength and modulus can be interpreted by the nanoclays role in the improvement of the load transfer from the matrix to the fiber and hence enhancement of the interfacial properties. This study confirmed that nanoclays can be used to upgrade the mechanical performance of natural fiber composites.

INTRODUCTION

With considerable awareness to preserve environment, sincere efforts across the globe look for renewable and bio-degradable sources of material available on the earth. The ultimate aim is to replace products which are derivatives of depleting resources of earth like petrol or high energy demanding and this had pushed the researchers to investigate the potential of natural fibers like flax as reinforcement material for composites.

Flax fibers show very good intrinsic mechanical properties, and low cost, low density (1.4-1.5 g/cm³), low dermal and respiratory irritation and tool wear, this allowed us to compare it with glass fibers. However, natural fiber does not exhibit consistency in properties and it widely depends upon their genotype, agriculture conditions, soil, topographic and climatic condition of the region. Besides that, several inherent properties of the flax fiber including hydrophilic nature, poor fiber and matrix adhesion, low heat stability and processing temperature hamper its long term stability in different engineering application under adverse environmental and designed conditions that limit its scope of utilization [1-4].

In fact, natural fiber is not a single filament and its properties widely depend upon their genotype, agriculture conditions, soil, topographic and climatic condition of the region. Further the method adopted to remove fibers from the plant stem dictates development of kink band or nodes [5] (found in cell wall) which is another decisive step in formulating physical and chemical properties of these fibers [6]. Besides that, hydrophilic nature of the natural fiber promotes the natural tendency of absorbing moisture. Water uptake and release cause swelling of the composite; this has detrimental effect on the dimensional stability of the composite [7]. Low heat stability and processing temperature of most of the naturally available fiber is limited to 200 °C for its optimum performance, this further limits its application. Long term stability of fiber and fiber-matrix adhesion also causes the limitations of the natural fiber application. Therefore, researchers constantly striving for their best efforts to overcome the limitations associated with the natural fiber composite and to make it a better reinforcement material for the manufacturing of composite for engineering applications [8-11].

This present work was carried to address some of the limitation of natural fibers to enhance the properties of the flax fiber epoxy composite. Different solutions for the improvement of the fiber-matrix interface were investigated.

EXPERIMENTAL

The epoxy resin used was the standard DGEBA (diglycidyl ether of bisphenol A) resin EPON[™] Resin 828 from Resolution Performance Products (Houston, TX, USA). The epoxy resin was cured with the polyoxypropylene diamine hardener Jeffamine® D-230 from Huntsman LLC (The Woodlands, TX, USA) at a level of 32 phr. The organoclay used was Cloisite® 30B from Southern Clay Products, Inc. (Gonzalez, TX, USA). Satin plain weave flax fabric was supplied by Moss Composites (Belgium). The epoxy-clay nanocomposite was prepared as described elsewhere [12].

Fiber properties can be modified in many ways including physical stretching, thermo-treatment etc. and chemical treatment. But surface properties are considerably changed by chemical treatment. Treatment of the fiber does not only affect the surface properties but it was also reported that micro fibrils rearrange themselves in the fiber [13]. In this work the fibers were treated with 2% solution of NaOH at 80 °C for 2 h. Fibers then were dried at room temperature for at least 6 hrs, then in the oven at temperature of 140 °C for about 2 hours to remove the humidity before use.

Empirical mixture of resin and hardener was prepared in a container and was manually mixed for 5 min. The mixture was subjected to a vacuum oven set at 65°C for 5 min for air removal. The mixture was then used to impregnate the flax fibers. After every two layers of fiber fabric, resin was spread evenly on the fibers and utmost care was taken to prevent any disturbance in the alignment or the straightness of the fibers.

Hydraulic press was used to fabricate the composites following specific temperature and pressure profiles (Figure 1). Composite descriptions are shown in Table I.

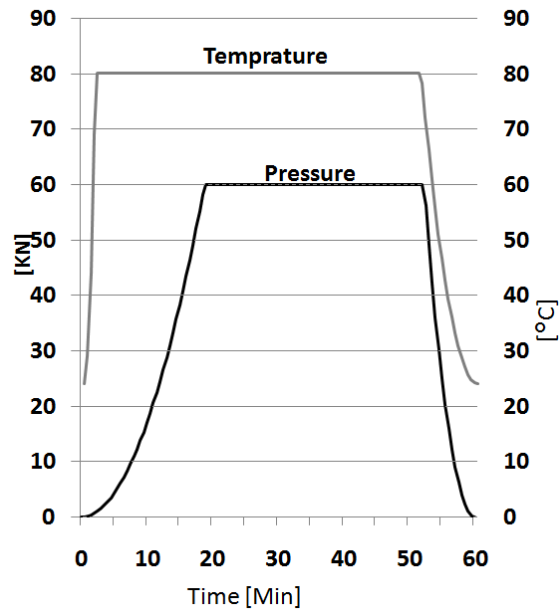


Figure 1. Optimized pressure and temperature profiles.

TABLE I. COMPOSITE DESCRIPTIONS


Designation	Description
NT-F+E	Non treated fibers with epoxy
NT-F+NC-E	Non treated fibers with epoxy nanocomposite
T-F+NC-E	Treated fibers with epoxy nanocomposite
T-F+E	Treated fibers with epoxy

The tensile and interlaminar shear strength properties of the epoxy/flax composites were determined at room temperature and 50% relative humidity according to ASTM D638-03 and ASTM D 2344-00 on an Instron 5500R machine, with crosshead speeds of 5.0 mm/min, 1.3 mm/min respectively.


JEOL JSM-6100 SEM working at a voltage of 10kV was used to observe the surface of fibers before and after treatment with NaOH. Fracture surfaces of composites after mechanical test were also analyzed by SEM.

RESULT AND DISCUSSIONS

SEM images of the flax fibers before and after treatment with 2% solution of NaOH are shown in Figure 2. SEM indicates that the surface of fiber before treatment was not clean and shows many lumps of contaminations on the surface as can be seen on Figure 2a. The result shows that after treatment of the fiber with 2% NaOH solution for 2 hrs at 80°C, the outer surface of the fibers is smooth. In addition, tow opening is also observed on the treated fibers.

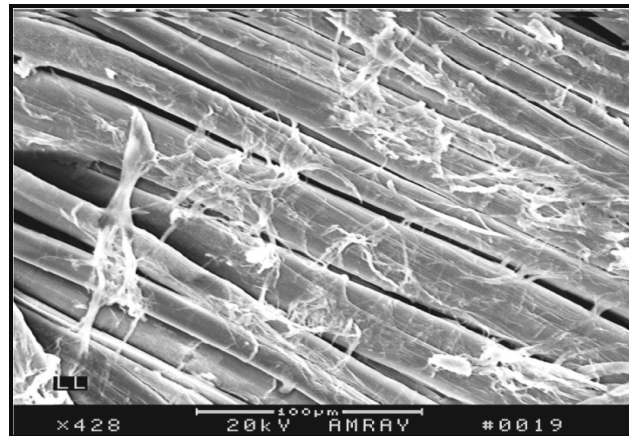

(a)

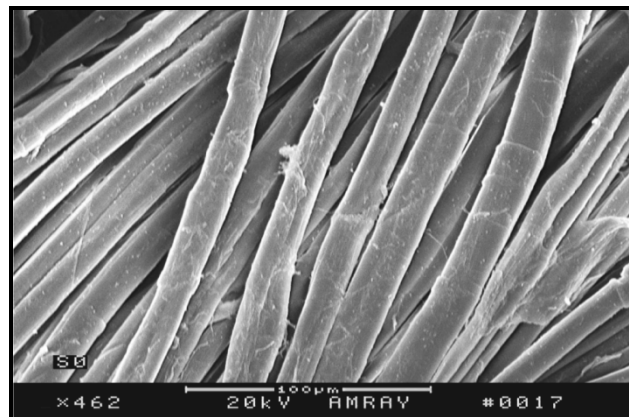

(b)

Figure 2. SEM photos for (a) non-treated and (b) treated flax fibers.

The tensile Properties of composites are shown in Figure 3. From the tensile property graphs it can be observed that the stress bearing capacity of the composite with the treatment of fibers increases to approximately 15 % and similarly there is an increase in the young's modulus and strain.

Moreover, there is also improvement in the mechanical properties when nanoclay is added to the matrix but that improvement diminished in comparison with composite having treated fibers. This is due to the poor level of impregnation and void formation

observed in the composites when the viscosity of the matrix increases with the addition of nanoclay particles.

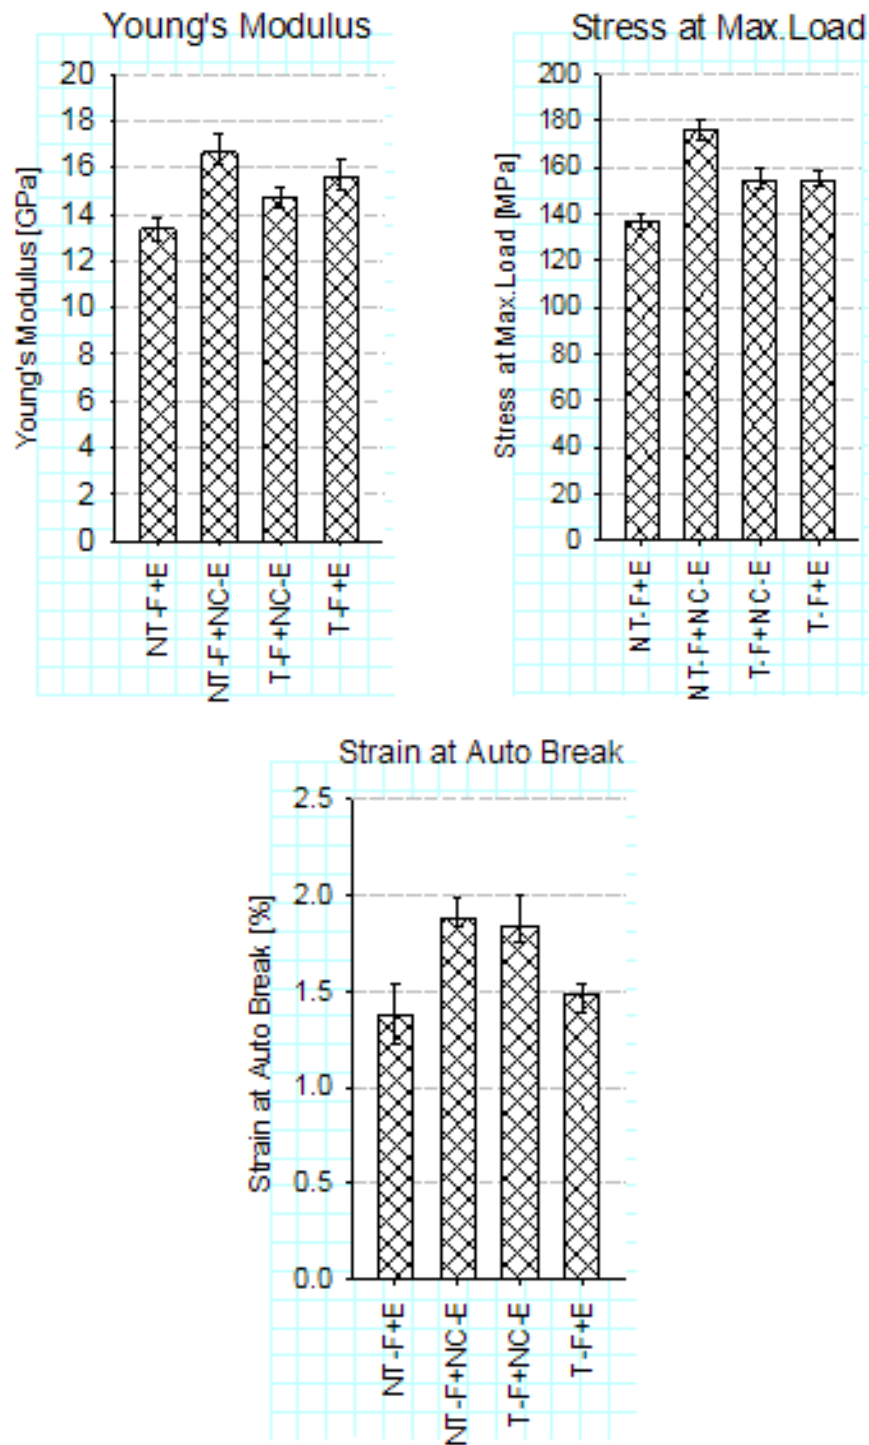


Figure 3. Tensile properties for different epoxy/flax composites

Figure 4 shows the short beam shear strength of the epoxy flax composites. Similar trend of improvement but higher level was observed in the results of short beam shear strength compared the tensile. An improvement of about 60% is observed for treated fibers and treated fibers in the presence of nanoclays. Again better results are found for non treated fibers in epoxy-clay nanocomposite matrix (approximately 85%).


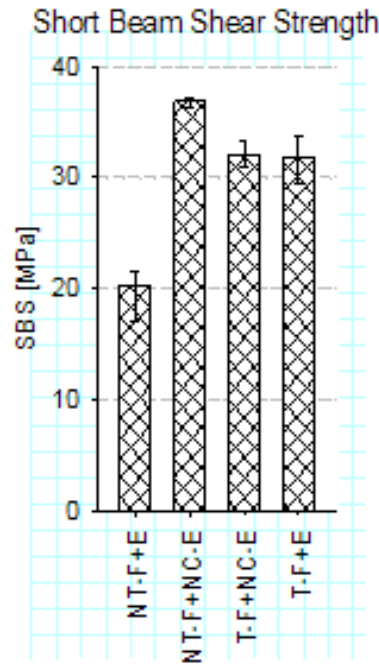


Figure 4. Short beam shear strength for different epoxy-flax composites


SEM images of the tensile fracture surface of specimen of flax fiber composites are shown in Figure 5. Figure 5a shows that the interfacial adhesion between flax fibers and epoxy matrix of composite is not so strong. The clean fibers were pulled out after test with clean fiber surface and not much adhering epoxy matrix on their surface. The clean and smooth cavities after the pulling of the fibers suggest poor interface. Figures 5b and 5c show that better surface contact is achieved between the fibers and the matrix in case of treated flax fiber epoxy composite. And, this seems much better for the non treated flax fiber epoxy in the presence of nanoclay. This good interfacial adhesion can improve the stress transfer ability from the matrix to the fiber, which results in a better mechanical property.



(a)

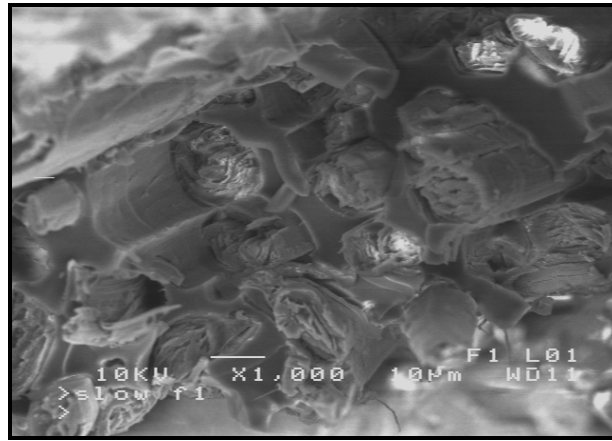

(b)

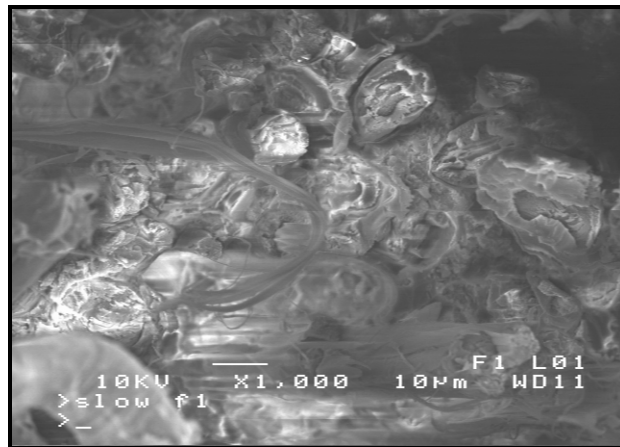

(c)

Figure 5. SEM micrographs for (a) non-treated flax epoxy composite, (b) treated flax epoxy composite; and (c) non-treated flax-epoxy nanocomposite

CONCLUSIONS

Introduction of nanoclay in the epoxy resin significantly improves the mechanical properties of the flax fiber composite. The observed improvements in composite

strength, modulus and short beam shear strength can be interpreted by the nanoclays role in the improvement of the load transfer from the matrix to the fibers and hence enhancement of the interfacial properties. This study confirms that nanoclays can be used to upgrade the mechanical performance of natural fiber composites. Treatment of the flax fibers with 2% alkaline solution for 2 hrs at 80°C has also an impact on the mechanical properties of the composites however the level is not high as the nanoclay.

ACKNOWLEDGEMENT

The authors would like to thank the financial support from different research programs of the Canadian Government via the National Research Council of Canada, the Agriculture Agri-Food Canada and the NRCan Canada.

REFERENCES

1. K. Van De Velde, & E. Baetens "Thermal and mechanical properties of flax fiber as potential composite reinforcement" *Macromolecular Material Engineering* 2001, 286, 342-349
2. G. Romhany, J. Karger-Kocsis, & T. Czigany "Tensile and fracture behaviour of technical flax fibers" *Journal of Applied Polymer Science* 2003, Vol 90, 3638-3645
3. A. J. Norton, S. J. Bennett, M. Hughes, J. P. R. E. Dimmock, D. Wright, G. Newman, I. M. Harris & G. Edwards-Jones "Determining the physical properties of flax fiber for industrial application: the influence of agronomic practice." *Annals of Applied Biology* 2006 Vol 149, 15-25
4. E. Zini, M. Baiardo, L. Armelao, & M. Scandola "Biodegradable polyesters reinforced with surface-modified vegetable fibers" *Macromolecular Bioscience* 2004, 286-295
5. A. J. Norton, S. J. Bennett, M. Hughes, J. P. R. E. Dimmock, D. Wright, G. Newman, I. M. Harris & G. Edwards-Jones "Determining the physical properties of flax fibre for industrial applications : the influence of agronomic practice" *Annals of Applied Biology* ISSN 0003-4746
6. R. Kohler, R. Alex, R. Brielmann, & B. Ausperger "A new kinetic model for water sorption isotherms of cellulosic materials" *Macromol. Symposium* 2006, 244, 89-96
7. G. Romhany, J. Karger-Kocsis, & T. Czigany "Tensile fracture and failure behaviour of thermoplastix starch with unidirectional and cross-ply flax fiber reinforcements" *Macromolecular Material and Engineering* 2003
8. S. G. Lee S.-S. Choi, W. H. Park, & D. Cho "Characterization of surface modified flax fiber and their biocomposites with PHB" *Macromolecular Symposium* 2003, Vol. 197, 89-99
9. M. J. A. Van Den Oever, H. L. Bos, & K. Molenveld "Flax fiber physical structure and its effect on composite properties: Impact strength and thermo-mechanical properties" *Die Angewandte Makromolekulare Chemie* 1999, 272, 71-76 (Nr. 4760)
10. I. Van de Weyenberg, T. Chi Truong, B. Vangrimde, & I. Verpoest "Improving the properties of UD flax fibre reinforced composites by applying an alkaline fibre treatment" *Composites Part-A Applied Science and Manufacturing* 2006, 37, 1368-1376
11. G. Romhany, J. Karger-Kocsis & Tibor Czigany "Tensile fracture and failure behaviour of thermoplastic starch with unidirectional and cross-ply flax fiber reinforcements" *Macromolecular Engineering* 2003, 288, No. 9, 699-707
12. T.-D. Ngo, M.-T. Ton-That, S.V. Hoa, K.C. Cole 2009, 49(4), 666-672.
13. A. Arbelaiz, G. Cantero, B. Fernandez, & I. Mondragon "Flax Fiber surface modification: Effects on fiber physic mechanical and flax /Polypropylene interface properties" *Society of Plastic Engineering* 2005