

## NRC Publications Archive Archives des publications du CNRC

### Thermal analysis of the $3\text{CaO} \cdot \text{Al}_2\text{O}_3\text{-CaSO}_4 \cdot 2\text{H}_2\text{O-CaCO}_3\text{-H}_2\text{O}$ system Ramachandran, V. S.; Zhang, C. M.

This publication could be one of several versions: author's original, accepted manuscript or the publisher's version. /  
La version de cette publication peut être l'une des suivantes : la version prépublication de l'auteur, la version  
acceptée du manuscrit ou la version de l'éditeur.

#### Publisher's version / Version de l'éditeur:

*Thermochimica acta*, 106, pp. 273-282, 1986

**NRC Publications Archive Record / Notice des Archives des publications du CNRC :**  
<https://nrc-publications.canada.ca/eng/view/object/?id=91864735-9f84-4438-9c48-c3a706f0c5ef>  
<https://publications-cnrc.canada.ca/fra/voir/objet/?id=91864735-9f84-4438-9c48-c3a706f0c5ef>

Access and use of this website and the material on it are subject to the Terms and Conditions set forth at  
<https://nrc-publications.canada.ca/eng/copyright>

READ THESE TERMS AND CONDITIONS CAREFULLY BEFORE USING THIS WEBSITE.

L'accès à ce site Web et l'utilisation de son contenu sont assujettis aux conditions présentées dans le site  
<https://publications-cnrc.canada.ca/fra/droits>

LISEZ CES CONDITIONS ATTENTIVEMENT AVANT D'UTILISER CE SITE WEB.

**Questions?** Contact the NRC Publications Archive team at  
PublicationsArchive-ArchivesPublications@nrc-cnrc.gc.ca. If you wish to email the authors directly, please see the  
first page of the publication for their contact information.

**Vous avez des questions?** Nous pouvons vous aider. Pour communiquer directement avec un auteur, consultez la  
première page de la revue dans laquelle son article a été publié afin de trouver ses coordonnées. Si vous n'arrivez  
pas à les repérer, communiquez avec nous à PublicationsArchive-ArchivesPublications@nrc-cnrc.gc.ca.

Ser  
TH1  
N21d  
no. 1416  
c. 2  
BLDG



**National Research  
Council Canada**

Institute for  
Research in  
Construction

**Conseil national  
de recherches Canada**

Institut de  
recherche en  
construction

## ***Thermal Analysis of the $3\text{CaO} \cdot \text{Al}_2\text{O}_3\text{-CaSO}_4 \cdot 2\text{H}_2\text{O-CaCO}_3\text{-H}_2\text{O}$ System***


by V.S. Ramachandran and Zhang Chun-Mei

Reprinted from  
Thermochimica Acta,  
Vol. 106, (1986)  
p. 273-282  
(IRC Paper No. 1416)

ANALYZED

Price \$2.00

NRCC 26639

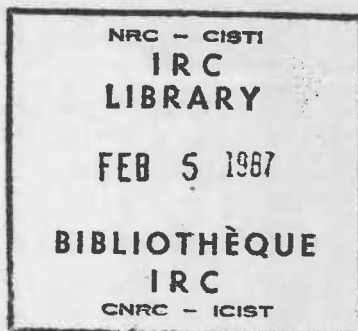

**Canada**

7073155

CISTI/ICIST



3 1809 00210 5986

# RÉSUMÉ

Les auteurs ont étudié, par calorimétrie différentielle à balayage et par thermogravimétrie, les produits d'hydratation formés à divers moments dans des mélanges contenant du  $C_3A$  et du  $CaSO_4 \cdot 2H_2O$  (0, 12,5, 25 %) ou du  $CaCO_3$  (0, 12,5, 25 %), ou les deux. Selon la durée de l'hydratation, différents produits se forment. L'hydratation inhibe la formation de  $C_3A$  et sa consommation d'un

## THERMAL ANALYSIS OF THE $3\text{CaO} \cdot \text{Al}_2\text{O}_3\text{--CaSO}_4 \cdot 2\text{H}_2\text{O--CaCO}_3\text{--H}_2\text{O}$ SYSTEM

V.S. RAMACHANDRAN and ZHANG CHUN-MEI \*

*Division of Building Research, National Research Council of Canada, Ottawa, K1A 0R6 (Canada)*

(Received 4 March 1986)

### ABSTRACT

Hydration products formed at different periods in mixtures containing  $\text{C}_3\text{A}$  with either or both  $\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$  (0, 12.5, 25%) and  $\text{CaCO}_3$  (0, 12.5, 25%) were followed by differential scanning calorimetry and thermogravimetry. Depending on the length of hydration, different products were formed. Calcium carbonate retards or suppresses formation of the cubic aluminate hydrate in the hydration of  $\text{C}_3\text{A}$ , but it accelerates the formation of ettringite and its conversion to the monosulfoaluminate phase in the hydration of  $\text{C}_3\text{A} + \text{gypsum}$ .

### INTRODUCTION

Calcium carbonate added to portland cement, as a partial replacement for cement, modifies early setting and hardening characteristics by influencing hydration of the  $\text{C}_3\text{A}$  phase.  $\text{CaCO}_3$  is known to form complexes with  $\text{C}_3\text{A}$ , as does gypsum. Attempts have also been made, therefore, to substitute part of gypsum by  $\text{CaCO}_3$ . Only limited data are available, however, pertaining to the role of  $\text{CaCO}_3$  in fresh concrete [1,2]. It was the objective of the present work to follow the hydration characteristics of  $\text{C}_3\text{A}$  and  $\text{C}_3\text{A} + \text{gypsum}$  in the presence of different amounts of finely divided  $\text{CaCO}_3$ .

### EXPERIMENTAL

#### *Equipment*

DSC and TGA curves were obtained using the Du Pont 1090 thermal analysis system. In each DSC experiment a 20-mg sample was heated in a

\* Visiting Scientist, Nanjing Institute of Technology, Nanjing, The People's Republic of China.

continuous flow of nitrogen gas from room temperature to 600°C at 20°C min<sup>-1</sup>. The TGA experiment was carried out by heating the samples to 1000°C. X-ray photographs were obtained by a Norelco unit using a Debye-Scherrer camera. The relative intensities of the lines were obtained by densitometer traces of the X-ray films.

### *Materials*

Tricalcium aluminate was supplied by the Tetrattech Co.; gypsum and calcium carbonate (N<sub>2</sub> surface area 6.5 m<sup>2</sup> g<sup>-1</sup>), both of reagent quality, were supplied by Fisher Scientific Co. and by Anachemia Chemical Co., respectively.

### *Sample preparation*

In all, eight mixes were prepared: (1) C<sub>3</sub>A containing no gypsum, (2) C<sub>3</sub>A + 12.5% gypsum, (3) C<sub>3</sub>A + 25% gypsum, (4) C<sub>3</sub>A + 12.5% CaCO<sub>3</sub>, (5) C<sub>3</sub>A + 25% CaCO<sub>3</sub>, (6) C<sub>3</sub>A + 12.5% gypsum + 12.5% CaCO<sub>3</sub>, (7) C<sub>3</sub>A + 25% gypsum + 12.5% CaCO<sub>3</sub> and (8) C<sub>3</sub>A + 25% gypsum + 25% CaCO<sub>3</sub>. The percentage of additive was based on the weight of C<sub>3</sub>A.

The dry powders were transferred to capped vials and glass beads were mixed into them using a Spex mixer for 3 min. Double-distilled water was added gradually and the mix was stirred at a water/C<sub>3</sub>A ratio of 4. At specified intervals (5, 10, 20, 30 min; 1, 2, 4, 7 h; and 1, 2, 3 days) the samples were removed for examination. Cold methanol was used to stop hydration at different intervals. The pastes were dried at room temperature under vacuum or at 50°C under vacuum.

## RESULTS AND DISCUSSION

### *Hydration of 3CaO · Al<sub>2</sub>O<sub>3</sub>*

Figure 1 shows DSC thermograms of C<sub>3</sub>A hydrated for periods varying from 5 min to 2 days. Even at 5 min, endothermal effects signifying the presence of hydration products are evident. Peaks at about 145–150 and 265–280°C represent the presence of a metastable hexagonal phase. As hydration progresses, the endothermal peak at about 150°C increases for up to 4 h, and that at about 265–300°C continues to increase up to 2 days. The large peak at about 300°C (4 h to 2 d) is due mainly to the presence of the cubic phase (C<sub>3</sub>AH<sub>6</sub>). The exact time of conversion of the hexagonal phase to the cubic phase is not easy to determine because the two co-exist. XRD results confirm the DSC results (Table 1).

TABLE 1

XRD lines of products formed at different times in the  $C_3A-CaCO_3-CaSO_4 \cdot 2H_2O-H_2O$  system

Material	Hydration period	Components detected							
		$C_3A$	Gypsum	$CaCO_3$	Hexagonal aluminate hydrate	Cubic aluminate hydrate	Ettringite	Monosulfoaluminate hydrate	Carboaluminate hydrate
$C_3A$	10 min	1	—	—	3	—	—	—	—
	1 h	2	—	—	2	4	—	—	—
	7 h	2	—	—	4	2	—	—	—
	2 d	4	—	—	—	1	—	—	—
$C_3A + 12.5\% CaCO_3$	10 min	1	—	2	—	—	—	—	2
	2 d	4	—	5	—	2	—	—	1
$C_3A + 12.5\% \text{ gypsum}$	30 min	1	4	—	—	—	4	—	—
	1 h	1	—	—	—	—	—	3	—
	7 h	3	—	—	4	4	—	2	—
	3 d	5	—	—	—	4	—	2	—
$C_3A + 12.5\% \text{ gypsum} + 12.5\% CaCO_3$	10 min	1	4	2	—	—	2	—	5
	20 min	1	—	2	—	—	—	4	5
	1 h	2	—	4	—	—	—	4	4
	7 h	2	—	5	—	—	—	4	2
	3 d	5	—	—	—	—	—	3	2

Numbers refer to the relative intensities of peaks: 1, very strong; 2, strong; 3, medium strong; 4, weak; 5, very weak.

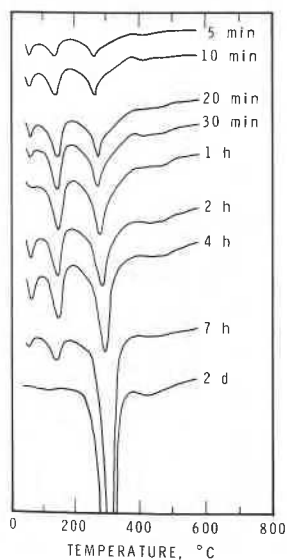


Fig. 1. DSC curves of  $C_3A$  hydrated for different periods.

#### *Hydration of $3CaO \cdot Al_2O_3 - CaCO_3$ mixture*

DSC curves of the products of hydration of  $C_3A - CaCO_3$  are different from those obtained with hydration of  $C_3A$  (Fig. 1-3). In the early periods endothermic peaks form at 150-160 and 235-245°C in the  $C_3A - CaCO_3$

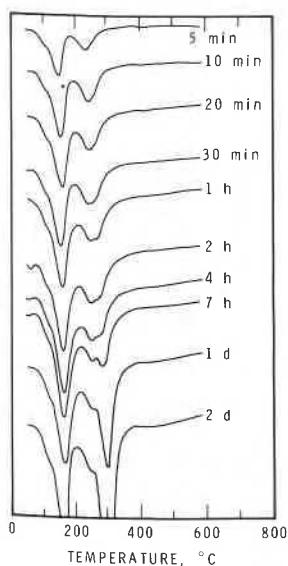


Fig. 2. DSC curves of  $C_3A$  hydrated for different periods in the presence of 12.5%  $CaCO_3$ .

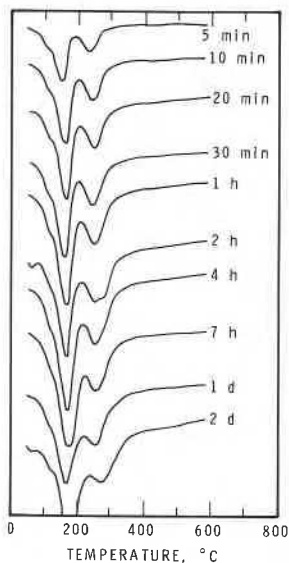


Fig. 3. DSC curves of  $C_3A$  hydrated for different periods in the presence of 25%  $CaCO_3$ .

mixture containing 12.5%  $CaCO_3$ . They may also be observed during the hydration of  $C_3A$  without  $CaCO_3$  (Fig. 1). The peaks, however, represent calcium carboaluminate (or a solid solution  $C_3A \cdot Ca(OH)_2 \cdot XH_2O$ – $C_3A$ – $CaCO_3 \cdot XH_2O$ ) [3]. XRD reveals no hexagonal phase ( $C_2AH_x$  or  $C_4AH_x$ ) in this system (Table 1). The formation of a small amount of cubic aluminate hydrate (peak at about 260–280°C) at 2 h and intensifying at 2 d is also evident (Fig. 2). In the presence of 12.5%  $CaCO_3$  carboaluminate (solid solution) and cubic phases seem to co-exist at 2 d. The addition of  $CaCO_3$  to  $C_3A$  seems to retard the formation of the cubic phase [4]. XRD results also suggest that in the presence of 12.5%  $CaCO_3$  the main phases at 2 d are carboaluminate and cubic hydrates.

Differential thermogravimetric results are in agreement with those of DSC and XRD (Fig. 4). In the mixtures containing 12.5%  $CaCO_3$ , two peaks appear below 250°C at 10 min, caused by the carboaluminate. Two additional peaks occur at 700–750°C (due to decomposition of  $CaCO_3$ ) and at 850–900°C (due to decomposition of the carboaluminate) [5]. The presence of cubic aluminate is indicated at 7 h and 2 d by peaks at about 300–315°C. The combined  $CaCO_3$  in the carboaluminate in the samples was determined by the peak areas occurring at 850–900°C. The amounts were 1.5, 6.0 and 8.2% at hydration periods of 10 min, 7 h and 2 d, respectively, signifying a steady increase in the amount of carboaluminate as hydration progresses.

In the  $C_3A$ – $CaCO_3$ – $H_2O$  system containing 25%  $CaCO_3$ , larger amounts of carboaluminate are formed than in that containing 12.5%  $CaCO_3$ , and there is no evidence of cubic aluminate hydrate for up to 2 days (Fig. 3). The formation of the cubic phase may possibly be retarded or suppressed by the



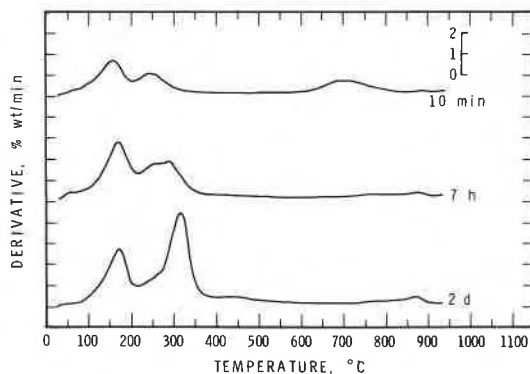


Fig. 4. Differential thermogravimetric curves of  $C_3A + 12.5\% \text{ CaCO}_3$  hydrated for different periods.

solid solution of carbonate. In the  $C_3A$ -lignosulfonate- $H_2O$  system a complex forms that is known to retard or suppress the conversion of the hexagonal to the cubic phase [6].

#### *Hydration of $3CaO \cdot Al_2O_3 - CaSO_4 \cdot 2H_2O$ mixtures*

In the system containing 12.5% gypsum, the gypsum is almost consumed at 30 min, as is evident by the decreasing intensity of the endothermic peak at  $130^\circ\text{C}$  (Fig. 5). XRD results indicate formation of the ettringite at 30

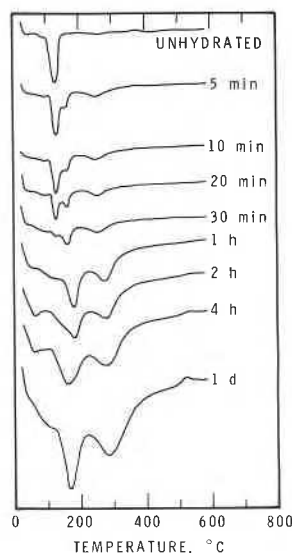


Fig. 5. DSC curves of  $C_3A$  hydrated for different periods in the presence of 12.5% gypsum.

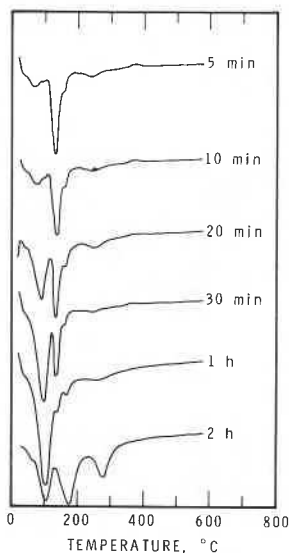


Fig. 6. DSC curves of  $C_3A$  hydrated for different periods in the presence of 25% gypsum.

min, after which the intensity of the endothermal peak at 165–180°C increases substantially. This peak represents monosulfoaluminate hydrate. XRD data confirm the presence of monosulfoaluminate hydrate at 1 h and after. From 7 h to 3 days monosulfoaluminate and some cubic phases are present (Table 1).

With 25% gypsum, ettringite can be detected even at 5 min (Fig. 6), the amount increasing with the time until between 1 and 2 h there is a sharp decrease. Gypsum is mostly consumed within 1 h, but at 12.5% gypsum it is consumed within 30 min.

#### *Hydration of $3CaO \cdot Al_2O_3 - CaSO_4 \cdot 2H_2O - CaCO_3$ mixtures*

In the system containing 12.5% gypsum and 12.5%  $CaCO_3$ , the rate of disappearance of gypsum seems to be accelerated by  $CaCO_3$  (Figs. 5 and 7). XRD results confirm that in the presence of  $CaCO_3$  gypsum is consumed within 20 min (Table 1). Comparison of the DSC curves for mixtures of  $C_3A + 25\%$  gypsum and  $C_3A + 25\%$  gypsum + 12.5%  $CaCO_3$  shows that gypsum is consumed more rapidly in the mixture containing  $CaCO_3$  (Figs. 6 and 8).

Formation of ettringite (peak at about 100°C) is accelerated by the addition of 12.5%  $CaCO_3$  to the mixture containing 12.5% gypsum. In the presence of  $CaCO_3$ , even at 10 min intense XRD lines of ettringite are evident (Table 1). DSC results also demonstrate that ettringite peaks occur within 5 min in the presence of  $CaCO_3$ , but not in the sample with only gypsum (Fig. 7). Examination of thermograms in Figs. 6 and 8 shows that

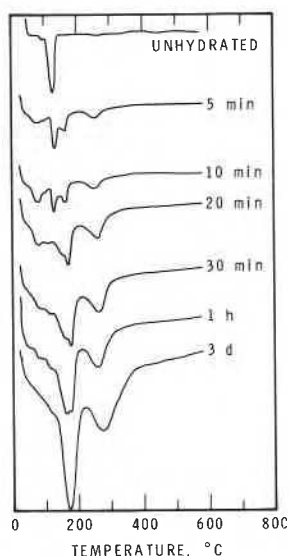


Fig. 7. DSC curves of  $C_3A$  hydrated for different periods in the presence of 12.5% gypsum + 12.5%  $CaCO_3$ .

the formation of ettringite is also accelerated by the addition of 12.5%  $CaCO_3$  to  $C_3A$  + 25% gypsum mixtures.

Conversion of ettringite to monosulfoaluminate is also accelerated by incorporation of  $CaCO_3$ . XRD results confirm this. Ettringite, which is

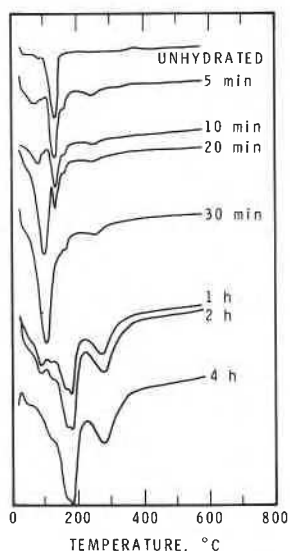


Fig. 8. DSC curves of  $C_3A$  hydrated for different periods in the presence of 25% gypsum + 12.5%  $CaCO_3$ .

detected at 30 min in the  $C_3A$ -gypsum mixtures, disappears within 20 min in the presence of  $CaCO_3$  (Table 1).

In the system with 25% gypsum and 12.5%  $CaCO_3$ , DSC thermograms indicate that most conversion occurs in the first 2 h, whereas with  $CaCO_3$  it occurs in about an hour. The conversion of ettringite to monosulfoaluminate is accelerated further at higher  $CaCO_3$  contents.

### *Role of $CaCO_3$*

In the  $C_3A$ -gypsum- $CaCO_3$  mixture the  $CaCO_3$  particles ( $6.5 \text{ m}^2 \text{ g}^{-1}$ ) are much finer than either the  $C_3A$  or gypsum particles (approximately  $0.5 \text{ m}^2 \text{ g}^{-1}$ ). The  $CaCO_3$  particles surround the  $C_3A$  and on contact with water the two react to form carboaluminate on the surface of the  $C_3A$ . This layer may be less compact and more permeable to water than ettringite, and will interfere with the formation of a more rigid layer of ettringite. It is known that the conversion of ettringite to monosulfoaluminate hydrate takes place after gypsum has been exhausted in the system. Calcium carboaluminate hydrate enhances the rate of consumption of gypsum and hence facilitates early conversion of ettringite to monosulfoaluminate.

### CONCLUSIONS

- (1) In  $C_3A$ - $H_2O$  mixtures, conversion to  $C_3AH_6$  is either suppressed or retarded by addition of  $CaCO_3$ .
- (2) The reaction between  $C_3A$  and gypsum to form ettringite is accelerated by the addition of  $CaCO_3$ .
- (3) Conversion of ettringite to monosulfoaluminate hydrate is accelerated by  $CaCO_3$ .
- (4) It is possible for ettringite, monosulfate, and carboaluminate to co-exist.

### ACKNOWLEDGEMENT

The authors are grateful to J. Clark, G.M. Polomark and P.J. Lefebvre for experimental assistance. This paper is a contribution from the Division of Building Research, National Research Council of Canada.

### REFERENCES

- 1 J. Bensted, *World Cem. Technol.*, 11 (1980) 395.
- 2 J. Bensted, *World Cem. Technol.*, 14 (1983) 383.

- 3 V.S. Ramachandran, *Application of Differential Thermal Analysis in Cement Chemistry*, Chemical Publishing Co., Inc., New York, 1969, 308 pp.
- 4 J. Jambor, 7th Int. Congr. Chem. Cem., Vol. IV, Paris, 1980, pp. 487-492.
- 5 M. Collepardi, S. Monosi, G. Moriconi and M. Pauri, *J. Am. Ceram. Soc.*, 68 (1985) 126.
- 6 V.S. Ramachandran and R.F. Feldman, *Mater. Struct.*, 5 (1972) 67.

This paper is being distributed in reprint form by the Institute for Research in Construction. A list of building practice and research publications available from the Institute may be obtained by writing to the Publications Section, Institute for Research in Construction, National Research Council of Canada, Ottawa, Ontario, K1A 0R6.

Ce document est distribué sous forme de tiré-à-part par l'Institut de recherche en construction. On peut obtenir une liste des publications de l'Institut portant sur les techniques ou les recherches en matière de bâtiment en écrivant à la Section des publications, Institut de recherche en construction, Conseil national de recherches du Canada, Ottawa (Ontario), K1A 0R6.